


Excellent Rubber Adhesion with Cobalt Salts of Versatic™ Acid 10



Versatic™ Acid 10 is a synthetic, highly branched tertiary carboxylic acid which provides excellent rubber to steel adhesion properties when formulated as a Cobalt salt in passenger car, truck and bus radial (TBR) tire applications. The outstanding rubber adhesion attributes combined with the high product quality and consistency contributes significantly to the safety profile of radial tires. The initial adhesion between rubber and tire cord in steel-belted radial tires is superior and the adhesion properties are maintained during usage under high temperature, humidity and corrosive conditions. Versatic Acid 10 is not subject to oxidative degradation in contrast to unsaturated natural acids that require more expensive refrigerated transportation.

Characteristics and Structure

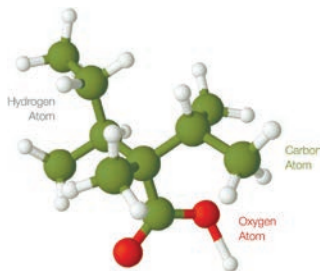

Acid value	318–330 mg KOH/g
Appearance	Clear liquid
Melting point	≤30°C

Benefits

- Significant contribution is made to the **safety profile** of radial tires when formulated as a Cobalt salt.
- **Superior initial adhesion** between rubber and steel cord with **excellent adhesion** properties is maintained during usage **under hot and humid conditions**.
- The synthetically manufactured product has a **high product quality** and **consistency**.
- The saturated molecule has **good storage stability** and is not subject to oxidative degradation.

Adhesion

The adhesion properties of Versatic Acid 10 as a Cobalt salt in a typical rubber formulation for a steel-belted

TBR tire have been measured versus a 20.5% Cobalt Neodecanoate commercial benchmark that is globally recognized as the industry standard. The Cobalt salt synthesis technology is proprietary to the Beijing Rubber Research and Design Institute and licensed for the Chinese market. It is based on Versatic Acids 10 and 5. All characterization and testing have been made according to standard methods.

Cobalt Salts Characterization

The characterization of the Cobalt salt synthesized from Versatic Acid 10 (Cobalt Versatate) is given in Table 1 and compared with the 20.5% Cobalt Neodecanoate commercial benchmark (Benchmark) and the market specifications. Cobalt content and softening point meet the market specifications.

Table 1: Cobalt Salt Characteristics

Property	Cobalt Versatate	Benchmark	Market specifications
Appearance	Brittle solid, blue-violet	Brittle solid, blue-violet	Brittle solid, blue-violet
Cobalt content (%)	20.7	20.4	20.5 ± 0.5
Softening point (°C)	87	92	90 ± 10
Heating loss test (%)	0.2	2.4	≤1.0

Formulation and Mixing Process

The test parameters are given in Table 2 and are typical for TBR belt formulations.

- Natural rubber is mixed (80 rpm) at 80°C in the Banbury for 1 minute, the temperature is about 90°C.
- After rubber additives addition which includes Zinc Oxide, Cobalt salt, antioxidant and rubber adhesives, mixing is carried out for 1.5 minute, the temperature is about 110°C, and carbon black is added and mixed over 3.5 minutes.
- The temperature is increased at 15°C/min for 3.5 minutes until 150-170°C at which point the mixture is discharged from the Banbury.
- The formulated rubber is transferred to a rubber mixing mill: after adding sulfur and accelerator, it is processed 5 times at 90-95°C.

The cure curves in Figure 1 illustrate very similar curing behavior for both formulations.

The vulcanized rubber has been characterized: hardness, elongation at break, tensile strength, tension permanent deformation, tensile stress at a given elongation and tear strength were measured. Results below in Table 3 for the Cobalt Versatate are very similar to those for the benchmark sample.

Table 2: Rubber Formulation

Component (in grams)	Cobalt Versatate	Benchmark
Natural rubber	100.0	100.0
Carbon black	53.5	53.5
Zinc Oxide	8.0	8.0
Antioxidant	3.5	3.5
Sulfur and Accelerator	6.4	6.4
Benchmark Cobalt salt	–	1.2
Cobalt Versatate	1.2	–
Rubber adhesives	5.7	5.7
Total (grams)	178.3	178.3

Figure 1: Mooney Viscosity Curves at 150°C Curing

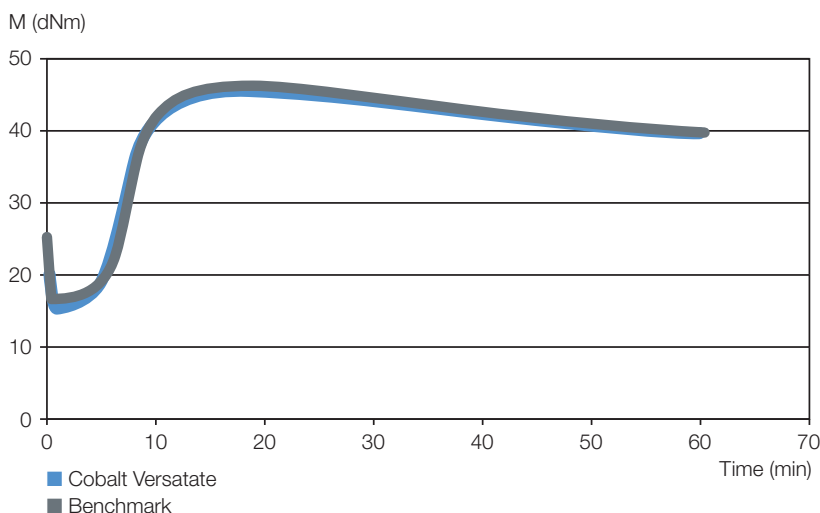


Table 3: Strength Test Results of Vulcanized Rubber Before Ageing

Physical properties of vulcanized rubber (150°C, 20 min)	Cobalt Versatate	Benchmark
Shore hardness	79	79
Elongation at break (%)	414	395
Tensile strength (MPa)	25	25
Tensile stress at a given elongation M ₁₀₀ (MPa)	6	6
Tensile stress at a given elongation M ₃₀₀ (MPa)	19	20
Tension permanent deformation (%)	20	20
Tear strength (kN/m)	56	57

Excellent Adhesion Performance

Initial adhesion at different curing conditions

To evaluate the robustness under different curing conditions, the H pull out force (N) has been determined for the below optimum (15 minutes curing at 150°C), optimum (30 minutes), slight over cure (40 minutes) and strong over cured samples (50 minutes). The rubber coating rate is greater than 95% (optical disc). As shown in Table 4, the variation trend versus curing time is very similar for the two samples.

Adhesion after ageing

The H pull out force (N) has also been determined after ageing under various conditions:

- Heat ageing (100°C for 24, 48 and 98 hours)
- Steam-heat ageing (60°C; 90% humidity for 24, 48 and 72 hours)
- Salt ageing (20% NaCl for 2 and 7 days)


The adhesion results obtained were compared with the initial results. See Figure 2 for the results. The variation trend of the H pull out force of both cured rubber are the same whatever the ageing conditions are. The rubber coating rate is greater than 95% (optical disc), before and after ageing. The results demonstrate the good performance of the Cobalt salt based on Versatic Acid 10 as a rubber to steel tire adhesion promoter.

Table 4: H Pull Out Force Under Different Curing Conditions

Curing time (minutes)	H pull out force (N)	
	Cobalt Versatate	Benchmark
15	907	869
30*	1231	1220
40	1178	1153
50	983	990

*Optimum curing conditions

Figure 2: H Pull Out Force of Vulcanized Rubber Before/After Ageing

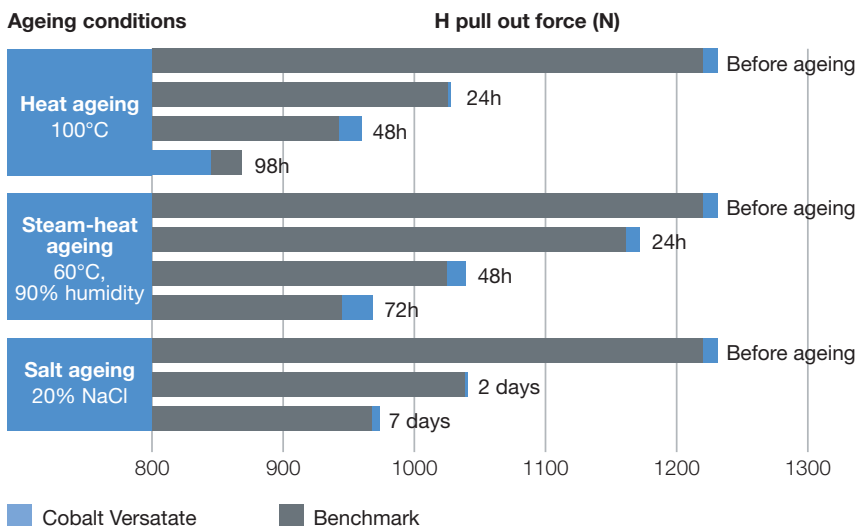

Conclusions

- Versatic Acid based Cobalt salt technology complies with the requirements of the global and local chemical industry standards.
- When using Versatic Acid 10 in a typical belt formulation for TBR, good rubber processing performance is obtained with very similar mechanical properties to the commercial Cobalt salt benchmark sample.
- Rubber to steel adhesion stays at a high level after ageing under high temperature, humidity and corrosive conditions.

Wherever you look a part of us is there.

We are pioneers of a higher chemistry. A chemistry designed to address the most pressing issues of our time. Forged from generations of invention and collaboration. Committed to safe manufacturing and community involvement. This powerful chemistry understands no boundaries, making it capable and responsible for shaping the future. This is the responsible path forward. This is what we call Responsible Chemistry.

Reach our Global Customer Service network at:

E-mail: service@hexion.com or enter a request on our website www.hexion.com under “contact us”

U.S., Canada and Latin America

+1 888 443 9466 / +1 614 986 2497

Europe, Middle East, Africa and India

+31 10 3136 500

China and Other Asia Pacific Countries

+86 21 3161 6680

Please refer to the literature code HXN-137 when contacting us.



World Headquarters

180 East Broad Street
Columbus, OH 43215-3799

© 2020 Hexion Inc. All rights reserved.

® and ™ denote trademarks owned or licensed by Hexion Inc.

HXN-137 12/22

The information provided herein was believed by Hexion Inc. (“Hexion”) to be accurate at the time of preparation or prepared from sources believed to be reliable, but it is the responsibility of the user to investigate and understand other pertinent sources of information, to comply with all laws and procedures applicable to the safe handling and use of the product and to determine the suitability of the product for its intended use. All products supplied by Hexion are subject to Hexion's terms and conditions of sale. HEXION MAKES NO WARRANTY, EXPRESS OR IMPLIED, CONCERNING THE PRODUCT OR THE MERCHANTABILITY OR FITNESS THEREOF FOR ANY PURPOSE OR CONCERNING THE ACCURACY OF ANY INFORMATION PROVIDED BY HEXION, except that the product shall conform to Hexion's specifications. Nothing contained herein constitutes an offer for the sale of any product.